

इंटरनेट

मानक

Disclosure to Promote the Right To Information

Whereas the Parliament of India has set out to provide a practical regime of right to information for citizens to secure access to information under the control of public authorities, in order to promote transparency and accountability in the working of every public authority, and whereas the attached publication of the Bureau of Indian Standards is of particular interest to the public, particularly disadvantaged communities and those engaged in the pursuit of education and knowledge, the attached public safety standard is made available to promote the timely dissemination of this information in an accurate manner to the public.

“जानने का अधिकार, जीने का अधिकार”

Mazdoor Kisan Shakti Sangathan


“The Right to Information, The Right to Live”

“पुराने को छोड़ नये के तरफ”

Jawaharlal Nehru

“Step Out From the Old to the New”

IS 7779-1-3 (1975): Schedule for properties and availability of stones for construction purposes, Part I: Gujarat state: Section 3 Engineering properties of stone aggregates [CED 6: Stones]

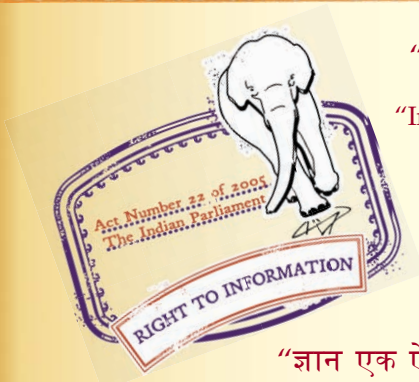

“ज्ञान से एक नये भारत का निर्माण”

Satyanarayan Gangaram Pitroda

“Invent a New India Using Knowledge”



“ज्ञान एक ऐसा खजाना है जो कभी चुराया नहीं जा सकता है”

Bhartrhari—Nitiśatakam

“Knowledge is such a treasure which cannot be stolen”

BLANK PAGE



IS : 7779 (Part I/Sec 3) - 1975

Indian Standard

SCHEDULE FOR PROPERTIES AND
AVAILABILITY OF STONES FOR
CONSTRUCTION PURPOSES

PART I GUJARAT STATE

Section 3 Engineering Properties of Stone Aggregates

UDC 691.21 : 691.22 (547.1) (083.4)



© Copyright 1975

INDIAN STANDARDS INSTITUTION
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG
NEW DELHI 110002

Price Rs 5.00

December 1975

Gr 3

Indian Standard

SCHEDULE FOR PROPERTIES AND AVAILABILITY OF STONES FOR CONSTRUCTION PURPOSES

PART I GUJARAT STATE

Section 3 Engineering Properties of Stone Aggregates

Stones Sectional Committee, BDC 6

Chairman

SHRI C. B. L. MATHUR

Representing

Public Works Department, Government of
Rajasthan, Jaipur

Members

SHRI K. K. AGRAWALA

Builders' Association of India, Bombay

SHRI K. K. MADHOK (*Alternate*)

SHRI T. N. BHARGAVA

Ministry of Shipping & Transport (Roads Wing)
Engineer-in-Chief's Branch (Ministry of Defence)

SHRI J. K. CHARAN

SHRI K. N. SUBBA RAO (*Alternate*)

CHIEF ARCHITECT

Central Public Works Department, New Delhi
National Test House, Calcutta

LALA G. C. DAS

SHRI P. R. DAS (*Alternate*)

SHRI Y. N. DAVE

Department of Geology & Mining, Government
of Rajasthan, Udaipur

SHRI R. G. GUPTA (*Alternate*)

DEPUTY DIRECTOR (RESEARCH),
CONTROL & RESEARCH LABORATORY

Public Works Department, Government of Orissa,
Bhubaneswar

DEPUTY DIRECTOR (RESEARCH)

Public Works Department, Government of Uttar
Pradesh, Lucknow

DR M. P. DHIR

Central Road Research Institute (CSIR),
New Delhi

SHRI R. L. NANDA (*Alternate*)

DIRECTOR, ERI

Public Works Department, Government of
Gujarat, Baroda

DIRECTOR (CSMRS)

Central Water Commission, New Delhi

DEPUTY DIRECTOR (CSMRS) (*Alternate*)

(Continued on page 2)

© Copyright 1975

INDIAN STANDARDS INSTITUTION

This publication is protected under the *Indian Copyright Act* (XIV of 1957) and reproduction in whole or in part by any means except with written permission of the publisher shall be deemed to be an infringement of copyright under the said Act.

IS : 7779 (Part I/Sec 3) - 1975

(Continued from page 1)

<i>Members</i>	<i>Representing</i>
DIRECTOR, MERI	Irrigation & Power Department, Government of Maharashtra, Bombay
RESEARCH OFFICER, MERI (<i>Alternate</i>)	
SHRI M. K. GUPTA	Himalayan Tiles & Marble Pvt Ltd, Bombay
SHRI S. D. PATHAK (<i>Alternate</i>)	
DR IQBAL ALI	Engineering Research Laboratory, Government of Andhra Pradesh, Hyderabad
SHRI A. B. LINGAM (<i>Alternate</i>)	
SHRI D. G. KADKADE	The Hindustan Construction Co Ltd, Bombay
SHRI V. B. DESAI (<i>Alternate</i>)	
SHRI T. R. MEHANDRU	Institution of Engineers (India), Calcutta
SHRI PREM SWARUP	Department of Geology & Mining, Government of Uttar Pradesh, Lucknow
SHRI A. K. AGARWAL (<i>Alternate</i>)	
DR A. V. R. RAO	National Buildings Organization, New Delhi
SHRI J. SEN GUPTA (<i>Alternate</i>)	
DR B. N. SINHA	Geological Survey of India, Calcutta
SHRI S. R. PRADHAN (<i>Alternate</i>)	
SUPERINTENDING ENGINEER (DESIGNS)	Public Works Department, Government of Tamil Nadu, Madras
DEPUTY CHIEF ENGINEER (I & D) (<i>Alternate</i>)	
SUPERINTENDING ENGINEER (DESIGN & PLANNING)	Public Works Department, Government of Andhra Pradesh, Hyderabad
SUPERINTENDING ENGINEER (DESIGNS)	Public Works Department, Government of Karnataka, Bangalore
SUPERINTENDING ENGINEER (PLANNING CIRCLE)	Public Works Department, Government of West Bengal, Calcutta
SUPERINTENDING SURVEYOR OF WORKS	Public Works Department, Government of Himachal Pradesh, Simla
SHRI D. AJITHA SIMHA, Director (Civ Engg)	Director General, ISI (<i>Ex-officio Member</i>)

Secretary

SHRI K. M. MATHUR
Deputy Director (Civ Engg), ISI

Indian Standard

SCHEDULE FOR PROPERTIES AND AVAILABILITY OF STONES FOR CONSTRUCTION PURPOSES

PART I GUJARAT STATE

Section 3 Engineering Properties of Stone Aggregates

0. FOREWORD

0.1 This Indian Standard (Part I/Section 3) was adopted by the Indian Standards Institution on 19 August 1975, after the draft finalized by the Stones Sectional Committee had been approved by the Civil Engineering Division Council.

0.2 Stones are available in large quantities in different parts of the country. To choose and utilize them for various uses, it is necessary to know their availability and also the strength properties determined according to the standard procedures. Accordingly, this Indian Standard is being formulated to cover this information for each State in the country. This standard will be published in parts, each part covering a State. For the facility of compiling and use of the standard, each part will be divided into three sections. Part I covers Gujarat State and will be issued in three sections. Section 1 gives information on the availability of stones in the form of map showing geological classification and known quarries; Section 2 covers engineering properties of building stones; and Section 3 covers engineering properties of stone aggregates. It is hoped that with the publication of this data it will be convenient for the users of stone to know not only the availability of stones but to select them in a scientific way depending upon the requirement for the particular use.

0.2.1 The information included in this Part covers data collected up to the end of 1974. Further information, as and when received, will be added as amendment to this standard.

0.3 The information contained in this Section is based on the data provided by the Engineering Research Institute (Public Works Department) of Gujarat State.

IS : 7779 (Part I/Sec 3) - 1975

0.4 In reporting the results of a test or analysis made in accordance with this standard, if the final value, observed or calculated, is to be rounded off, it shall be done in accordance with IS : 2-1960*.

1. SCOPE

1.1 This standard (Part I/Section 3) covers the engineering properties of stone aggregates in Gujarat State.

2. TEST RESULTS

2.1 The test results of most of the types of stone aggregates collected for some of the important properties according to relevant Indian Standards are given in Table 1.

*Rules for rounding off numerical values (*revised*).

TABLE 1 SCHEDULE OF CHARACTERISTICS OF STONE AGGREGATES — GUJARAT STATE

(Clause 2.1)

SL No.	LOCATION	TYPE OF AGGREGATE	APPARENT SPECIFIC GRAVITY IS : 2386 (Part III)-1963*	WATER ABSORPTION % IS : 2386 (Part III)-1963*	CRUSHING VALUE % IS : 2386 (Part IV)-1963†	ABRASION VALUE % IS : 2386 (Part IV)-1963†	IMPACT VALUE % IS : 2386 (Part IV)-1963†
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)
AMRELI							
1.	Amreli	Basalt	2.92	0.51	12.00	13.00	11.00
2.	Dhari	do	2.86	0.37	11.80	12.60	9.50
3.	Mahigigsagar	do	2.95	0.66	14.50	19.20	9.10
4.	Munjiasar	do	2.98	0.31	16.00	20.00	15.00
5.	Rajula	Trachyte	2.47	0.23	18.40	19.50	16.00
6.	Zar	Basalt	2.93	0.70	15.40	12.60	9.50
BANASKANTHA							
7.	Atal	Calc-gneiss	2.76	0.67	25.90	32.45	20.70
8.	Bhakar	Granite	2.64	0.40	26.50	26.10	24.80
9.	Budha Mahadeo	Limestone	2.59	1.36	58.00	32.00	33.70
10.	do	Sandstone	2.51	0.88	34.23	41.89	36.36
11.	Chitrangan	Basalt	2.91	0.40	15.00	16.30	8.00
12.	Dabhav	Gneiss	2.67	0.63	24.30	18.20	29.40
13.	Dantiwada	Gravel	2.65	0.93	27.90	46.40	25.90
14.	Deolinivav	Granite	2.70	1.76	22.80	20.70	25.30
15.	Eval	do	2.66	1.30	21.40	22.10	20.20
16.	Gola	do	2.62	1.30	31.00	14.50	32.60
17.	Khamiana	Sandstone	2.62	0.76	21.90	36.10	24.60
18.	Koteshwar	Granite	2.63	1.01	17.90	19.00	16.50
19.	Malachi	Limestone	2.57	1.85	23.10	31.70	24.30
20.	Malana	Quartzite	2.64	0.86	18.27	17.93	19.96
21.	Morra	Basalt	2.83	0.43	18.70	19.40	19.70
22.	Pavati	Granite	2.66	0.97	28.70	47.20	30.50
23.	Phangli	Basalt	2.95	0.90	19.70	—	—
24.	Rampur Mahudi	Calc-gneiss	2.83	0.15	25.40	26.60	25.50
25.	Sedhain	Limestone	2.60	0.44	24.80	36.20	25.60
BARODA							
26.	Agar	Sandstone	2.44	1.85	29.25	39.67	32.56
27.	Depsa	Basalt	2.99	1.56	14.40	13.90	12.50
28.	Kankpodia	Quartzite	2.61	0.37	28.30	45.13	26.10
29.	Ladi	Basalt	2.96	0.15	12.50	10.55	8.10
30.	Limbani	Granite	2.62	0.29	19.10	12.39	15.70
31.	Lothan	Quartzite	2.63	0.19	30.42	36.60	30.96
32.	Tejgadh	Granite	2.64	0.17	26.01	21.60	25.57
33.	Waghodia	Quartzite	2.60	0.29	15.50	16.00	14.00

*Methods of test for aggregates for concrete: Part III Specific gravity, density, voids, absorption and bulking.

†Methods of test for aggregates for concrete: Part IV Mechanical properties.

(Continued)

TABLE 1 SCHEDULE OF CHARACTERISTICS OF STONE AGGREGATES — GUJARAT STATE — *Contd*

Sl. No.	LOCATION	TYPE OF AGGREGATE	APPARENT SPECIFIC GRAVITY IS : 2386 (Part III)-1963*	WATER ABSORPTION % IS : 2386 (Part III)-1963*	CRUSHING VALUE % IS : 2386 (Part IV)-1963†	ABRASION VALUE % IS : 2386 (Part IV)-1963†	IMPACT VALUE % IS : 2386 (Part IV)-1963†
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)
BHAVNAGAR							
34.	Gordaka	Basalt	2.74	1.44	16.80	19.60	15.27
35.	Madandhar	do	2.77	0.97	12.76	11.75	12.12
36.	Mampur	do	2.73	0.87	14.40	14.20	13.05
37.	Sanjana	do	2.84	0.31	11.30	12.00	10.00
38.	Vijapaoj	do	2.76	1.37	15.50	17.50	12.03
BROACH							
39.	Dajipura	Basalt	2.96	0.44	11.60	—	5.40
40.	Garudeshwar	Gravel	2.89	0.66	11.20	13.20	7.10
41.	Koop	do	3.23	0.70	12.80	—	7.30
42.	Koyalivav	do	2.93	0.60	15.80	—	9.80
43.	Lilawadhar	do	2.89	0.70	10.80	—	7.80
44.	Mota Surva	Basalt	2.87	1.01	—	13.00	10.00
45.	Netrang	do	2.90	1.20	22.50	16.77	—
46.	Thuva	Gravel	2.91	1.03	22.00	—	15.80
47.	Tilakwada	do	2.87	0.83	13.80	26.70	11.30
48.	Trimroliia	do	2.98	0.50	16.30	—	9.80
49.	Zaria	do	2.89	0.86	12.50	18.70	9.10
DANGS							
50.	Chinchavgao	Basalt	2.93	0.76	13.10	15.40	10.70
51.	Nandiarā	do	2.91	0.41	12.90	12.70	8.60
52.	Saputara	do	2.92	0.43	13.10	12.20	10.36
53.	Takalipada	do	2.79	0.89	14.90	13.40	14.10
JAMNAGAR							
54.	Dhunvan	Basalt	2.79	1.94	20.00	22.40	18.00
55.	Dwarka	Limestone	2.60	0.70	28.80	36.30	24.50
56.	Hapadhar	Basalt	2.86	1.00	15.00	16.50	13.00
57.	Khariberaja	do	2.79	1.25	22.20	22.20	19.10
58.	Khuria	do	2.72	2.12	21.20	22.10	20.50
59.	Nagari	do	2.85	0.31	16.70	14.70	13.50
60.	Paliadhar	do	2.88	1.05	13.09	15.10	9.70
61.	Sachna	do	2.78	1.58	22.00	23.00	21.00
62.	Tarang	do	2.87	0.75	17.30	18.40	12.90
63.	Theba	do	2.76	1.75	23.20	23.60	19.40

*Methods of test for aggregates for concrete: Part III Specific gravity, density, voids, absorption and bulking.

†Methods of test for aggregates for concrete: Part IV Mechanical properties.

(Continued)

TABLE 1 SCHEDULE OF CHARACTERISTICS OF STONE AGGREGATES — GUJARAT STATE — *Contd*

SL No.	LOCATION	TYPE OF AGGREGATE	APPARENT SPECIFIC GRAVITY IS : 2386 (Part III)-1963*	WATER ABSORPTION % IS : 2386 (Part III)-1963*	CRUSHING VALUE % IS : 2386 (Part IV)-1963†	ABRASION VALUE % IS : 2386 (Part IV)-1963†	IMPACT VALUE % IS : 2386 (Part IV)-1963†
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)
JUNAGADH							
64.	Chhaya	Miliolite	2.61	0.80	23.90	27.00	33.80
65.	Gupta Prayag	Limestone	2.57	0.94	34.85	27.60	23.30
66.	Kalvad	do	2.78	1.30	11.00	10.50	10.00
67.	Kachhadi	Basalt	2.62	0.92	22.30	25.80	25.40
68.	Lalpur	Miliolite	2.78	1.19	12.50	12.00	11.00
69.	Palaghad	Basalt	2.62	1.25	27.20	23.60	25.20
70.	Porbandar	Limestone	2.63	2.00	17.80	14.40	15.00
71.	Ranavav	do	2.51	—	24.60	26.00	25.50
72.	Vakaria	Basalt	2.80	1.02	11.00	10.00	9.00
KAIRA							
73.	Angadi	Basalt	2.68	1.92	20.10	—	23.10
74.	Balasinor	Limestone	2.68	0.70	22.90	21.30	18.60
75.	Chitilav	Gravel	2.74	1.10	15.90	—	19.40
76.	Dakor	Sandstone	2.61	0.73	24.45	22.96	23.04
77.	Rozawa	Limestone	2.66	0.57	23.33	—	13.61
78.	Sevalia	Basalt	2.87	0.68	14.22	11.50	11.04
79.	Tayabpura	Limestone	2.53	2.80	35.89	—	31.45
80.	Vasad	Gravel	2.71	0.47	16.80	27.90	25.90
KUTCH							
81.	Bhujia Dungar	Basalt	3.05	0.66	11.40	12.60	9.90
82.	Chitrod	do	2.97	0.46	14.10	9.40	10.10
83.	Dhanai	do	2.88	0.97	14.00	20.00	—
84.	Kankeri	do	2.93	1.00	17.30	18.50	17.30
85.	Kukma	do	2.82	1.20	13.10	17.50	13.10
86.	Manjal	do	2.83	0.33	18.50	12.80	20.10
87.	Netra	do	2.83	0.63	16.20	17.00	15.20
88.	Vamoti	do	2.92	0.67	11.00	13.30	9.30
89.	Vondh	do	2.96	0.63	16.30	11.30	10.80
MEHSANA							
90.	Hatheli	Granite	2.66	0.48	22.80	19.10	20.80
91.	Kheralu	do	2.64	0.46	24.00	22.20	21.20
92.	Wadhali	do	2.65	0.47	17.64	10.27	13.80

*Methods of test for aggregates for concrete: Part III Specific gravity, density, voids, absorption and bulking.

†Methods of test for aggregates for concrete: Part IV Mechanical properties.

(Continued)

TABLE 1 SCHEDULE OF CHARACTERISTICS OF STONE AGGREGATES — GUJARAT STATE — *Contd*

SL No.	LOCATION	TYPE OF AGGREGATE	APPARENT SPECIFIC GRAVITY IS : 2386 (Part III)-1963*	WATER ABSORPTION % IS : 2386 (Part III)-1963*	CRUSHING VALUE % IS : 2386 (Part IV)-1963†	ABRASION VALUE % IS : 2386 (Part IV)-1963†	IMPACT VALUE % IS : 2386 (Part IV)-1963†
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)
PANCHMAHALS							
93.	Ankali	Limestone	2.56	2.60	26.37	31.62	23.00
94.	Asardi	Quartzite	2.63	0.40	18.68	20.33	12.80
95.	Bajarwada	Basalt	2.84	0.78	14.37	15.27	7.26
96.	Bhadalwada	Quartzite	2.62	0.16	18.38	22.37	19.31
97.	Chhaen	Limestone	2.59	1.69	20.43	21.60	13.18
98.	Chhapadi	Basalt	2.89	1.26	12.75	13.98	8.50
99.	Dabhavav	Limestone	2.65	1.16	26.42	31.50	24.00
100.	Dalwada	Quartzite	2.65	0.20	14.00	16.00	13.10
101.	Dhakalia	do	2.64	0.20	17.00	19.00	15.50
102.	Dungaria	do	2.62	0.70	23.30	20.00	25.10
103.	Godhra	Granite	2.61	0.25	21.00	23.00	16.00
104.	Halol	Basalt	2.80	0.67	16.00	17.50	15.00
105.	Jamotra	Quartzite	2.66	0.53	30.40	24.50	33.60
106.	Juna Baria	do	2.59	0.60	23.20	29.90	22.77
107.	Kadana	do	2.62	0.63	20.20	22.00	18.22
108.	Kadana	Gravel	2.83	0.39	11.69	35.93	10.60
109.	Kalikojava	Phyllite	2.68	1.77	32.58	51.72	34.48
110.	Kathala	Quartzite	2.65	0.21	21.88	26.27	16.18
111.	Khabda	Quartzite	2.63	0.20	17.14	24.70	12.70
112.	Kund	Basalt	2.84	1.28	15.00	18.00	13.00
113.	Limdi	Basalt	2.84	1.16	11.16	12.93	18.21
114.	Natapur	Quartzite	2.62	0.36	17.75	22.50	12.08
115.	Panchwada	do	2.63	0.53	19.37	22.88	18.47
116.	Pania	do	2.63	0.50	20.82	21.01	19.86
117.	Parwadi	Granite	2.62	0.39	22.32	17.68	13.15
118.	Pasaro	Quartzite	2.61	1.97	—	40.26	19.88
119.	Patoajol	Limestone	2.61	1.29	27.82	34.22	21.84
120.	Pavagadh	Volcanic breccia	2.50	2.31	21.50	24.00	17.90
121.	Rajula	Quartzite	2.69	0.17	17.00	24.41	19.75
122.	Raliata	do	2.63	0.21	20.16	18.46	14.88
123.	Sant	do	2.61	0.48	15.49	17.13	20.50
124.	Sharada	Limestone	2.62	2.08	11.89	27.17	15.57
125.	Simlia	Quartzite	2.61	0.65	20.37	27.88	16.37
126.	Vardhari	Granite	2.61	0.52	16.40	21.20	20.60

*Methods of test for aggregates for concrete: Part III Specific gravity, density, voids, absorption and bulking.

†Methods of test for aggregates for concrete: Part IV Mechanical properties.

(Continued)

TABLE 1 SCHEDULE OF CHARACTERISTICS OF STONE AGGREGATES — GUJARAT STATE — *Contd*

SL No.	LOCATION	TYPE OF AGGREGATE	APPARENT SPECIFIC GRAVITY IS : 2386 (Part III)-1963*	WATER ABSORPTION % IS : 2386 (Part III)-1963*	CRUSHING VALUE % IS : 2396 (Part IV)-1963†	ABRASION VALUE % IS : 2386 (Part IV)-1963†	IMPACT VALUE % IS : 2386 (Part IV)-1963†
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)
RAJKOT							
127.	Andasda	Basalt	2.93	0.44	12.30	13.70	8.20
128.	Chakodakhan	do	2.74	0.90	14.50	15.00	14.20
129.	Dharampur	do	2.95	0.54	14.60	13.60	10.90
130.	Ghunta	do	2.90	0.50	13.90	16.00	10.50
131.	Haripur	do	2.90	0.34	9.50	10.00	9.00
132.	Jamkandorna	do	2.84	0.55	11.00	12.30	10.00
133.	Keshod	do	2.72	0.73	13.10	14.90	10.30
134.	Khareda	do	2.95	0.13	12.80	13.10	10.00
135.	Khokhadod	do	2.87	0.71	12.00	13.00	9.13
136.	Lajai	do	2.87	0.79	9.76	11.50	8.57
137.	Lalपुर	do	2.93	0.13	12.30	13.00	9.60
138.	Mahendranagar	do	2.89	0.52	13.00	19.70	10.70
139.	Mahika	do	2.89	0.54	9.00	10.10	9.50
140.	Mauva	Basalt	2.89	0.82	10.50	11.00	9.50
141.	Motada	do	2.88	0.53	9.50	10.50	9.00
142.	Navagam	do	2.93	0.43	9.50	10.00	8.50
143.	do	Sandstone	2.30	4.28	47.60	63.60	45.30
144.	Raiya	Basalt	2.89	0.95	12.00	12.80	10.09
145.	Ribda	do	2.96	0.43	9.00	9.30	8.40
146.	Sapur	do	2.95	0.54	8.00	9.00	7.60
147.	Unchimandal	do	2.89	0.60	12.30	13.20	10.30
148.	Viren	do	2.69	0.77	14.60	16.20	12.80
SABARKANTHA							
149.	Balavam	Granite	2.60	0.73	31.74	25.93	36.94
150.	Evala	do	2.64	0.19	—	27.75	23.26
151.	Gambhirpura	do	2.61	0.17	32.14	43.86	28.63
152.	Himatnagar	do	2.67	0.25	24.60	23.50	—
153.	Hirpur	Gravel	2.64	1.00	28.80	30.40	28.60
154.	Idar	Granite	2.63	0.52	34.28	55.45	31.00
155.	Jamla	do	2.59	0.23	32.10	—	39.00
156.	Jankani	do	2.59	0.57	14.61	19.61	16.41
157.	Kapoda	Basalt	2.92	1.33	22.00	31.00	28.00
158.	Laloda	Granite	2.59	0.86	23.16	17.10	19.23
159.	Likhi	do	2.67	0.12	18.91	21.02	18.10
160.	Malasa	Limestone	2.76	0.67	19.70	13.90	18.00
161.	Panpur	Sandstone	2.45	4.00	31.90	31.96	22.20
162.	Rajpura	Basalt	2.71	2.84	14.90	13.40	11.00
163.	Vadagam	do	2.89	0.40	13.80	17.80	12.80
164.	Watrak	do	2.91	0.70	12.70	9.80	16.20

*Methods of test for aggregates for concrete: Part III Specific gravity, density, voids, absorption and bulking.

†Methods of test for aggregates for concrete: Part IV Mechanical properties.

(Continued)

TABLE 1 SCHEDULE OF CHARACTERISTICS OF STONE AGGREGATES — GUJARAT STATE — *Contd*

Sl No.	LOCATION	TYPE OF AGGREGATE	APPARENT SPECIFIC GRAVITY IS : 2386 (Part III)-1963*	WATER ABSORPTION % IS : 2386 (Part III)-1963*	CRUSHING VALUE % IS : 2386 (Part IV)-1963†	ABRASION VALUE % IS : 2386 (Part IV)-1963†	IMPACT VALUE % IS : 2386 (Part IV)-1963†
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)
SURAT							
165.	Ambhata	Basalt	2.86	0.66	11.60	11.60	11.40
166.	Areth	do	2.89	0.60	9.86	17.30	8.30
167.	Bamanwel	do	2.93	0.73	12.60	14.40	11.00
168.	Chhacharbunda	Dolerite	3.00	0.57	10.30	9.24	10.57
169.	Dungari	Basalt	2.87	0.63	12.60	14.30	13.20
170.	Duwada	do	2.92	0.46	13.40	10.40	10.40
171.	Gadat	Gravel	2.88	0.98	13.90	29.10	18.10
172.	Lukad	Basalt	2.96	1.34	17.20	18.00	16.00
173.	Maipur	do	2.89	0.70	12.90	—	8.40
174.	Nogama	do	2.90	0.73	10.99	12.29	9.75
175.	Pokhran	do	2.88	2.56	16.30	—	9.90
176.	Ukai	Gabbodiorite	3.00	0.53	12.01	10.20	10.24
177.	do	Basalt	2.89	0.41	11.49	8.86	9.05
SURENDRANAGAR							
178.	Chuda	Basalt	2.90	1.00	13.00	15.60	—
179.	Datar	do	2.91	0.80	22.20	12.10	15.50
180.	Kharava	Sandstone	2.37	3.75	44.00	59.50	50.70
181.	Khimiana	do	2.56	1.40	26.60	30.90	24.60
182.	Sayla	Basalt	2.86	1.30	12.66	16.00	10.00

*Methods of test for aggregates for concrete: Part III Specific gravity, density, voids, absorption and bulking.

†Methods of test for aggregates for concrete: Part IV Mechanical properties.

INDIAN STANDARDS ON STONES

IS :

- 1121 Method of test for determination of strength properties of natural building stones:
 - 1121 (Part I)-1974 Compression strength (*first revision*)
 - 1121 (Part II)-1974 Transverse strength (*first revision*)
 - 1121 (Part III)-1974 Tensile strength (*first revision*)
 - 1121 (Part IV)-1974 Shear strength (*first revision*)
- 1122-1974 Method of test for determination of specific gravity of natural building stones (*first revision*)
- 1123-1974 Method of identification of natural building stones (*first revision*)
- 1124-1974 Method of test for determination of water absorption apparent specific gravity and porosity of natural building stones (*first revision*)
- 1125-1974 Method of test for determination of weathering of natural building stones (*first revision*)
- 1126-1974 Method of test for determination of durability of natural building stones (*first revision*)
- 1127-1970 Recommendations for dimensions and workmanship of natural building stones (*first revision*)
- 1128-1974 Limestone slabs (*first revision*)
- 1129-1972 Recommendations for dressing of natural building stones (*first revision*)
- 1130-1969 Marble (blocks, slabs and tiles)
- 1706-1972 Method for determination of resistance to wear by abrasion of natural building stones (*first revision*)
- 1805-1973 Glossary of terms relating to building stones: quarrying and dressing (*first revision*)
- 3316-1974 Structural granite (*first revision*)
- 3620-1966 Laterite stone block for masonry
- 3622-1966 Sandstone slabs for use in flooring
- 4121-1967 Method of test for determination of water transmission rate by capillary action through natural building stones
- 4122-1967 Method of test for surface softening of natural building stones by exposure to acidic atmospheres
- 4348-1973 Method of test for determination of permeability of natural building stones (*first revision*)
- 5218-1969 Method of test for toughness of natural building stones
- 5640-1970 Method of test for determining the aggregate impact value of soft coarse aggregates
- 6241-1971 Method of test for determination of stripping value of road aggregates
- 6250-1971 Roofing slate tiles
- 6579-1972 Coarse aggregates for water bound macadam

INDIAN STANDARDS INSTITUTION

Manak Bhavan, 9 Bahadur Shah Zafar Marg, NEW DELHI 110002

Telephone : 27 01 31 (20 lines)

Telegrams : Manaksanstha

Regional Offices:

		Telephone
Western :	Novelly Chambers, Grant Road	BOMBAY 400007 37 97 29
Eastern :	5 Chowringhee Approach	CALCUTTA 700072 23-08 02
Southern :	54 General Patters Road	MADRAS 600002 8 37 81

Branch Offices:

'Pushpak', Nurmohamed Shaikh Marg, Khanpur	AHMEDABAD 380001	2 03 91
'F' Block, Unity Bldg, Narasimharaja Square	BANGALORE 560002	2 76 49
Kothi No. 90, Sector 18A	CHANDIGARH 160018	2 83 20
5-8-56/57 Nampally Station Road	HYDERABAD 500001	4 57 11
117/418 B Sarvodaya Nagar	KANPUR 208005	82 72
B.C.I. Bldg (Third Floor), Gandhi Maidan East	PATNA 800004	2 56 55